

Magnesium aluminate spinel raw materials for high performance refractories for steel ladles

Dagmar Schmidtmeier, Gunter Büchel, Andreas Buhr

Almatis GmbH

e-mail: dagmar.schmidtmeier@almatis.com, Gunter.Buechel@almatis.com

Abstract

High quality steel production requires extended treatment of the steel in the steel ladle. This has a remarkable impact on the steel ladle refractories, e.g. the need for high performance functional refractories like purging plugs. Operational changes such as increasing tapping temperatures, longer hold times and more aggressive secondary metallurgy are countered by the need for thinner refractory linings and longer refractories life. These combined factors have led to a resurgence in interest in magnesium aluminate spinel raw materials.

Magnesium aluminate spinels have been used in steel-making refractories for many years, in a variety of different forms. This paper reviews the production, properties and performance of spinels. Recent developments in the applications of spinels will also be discussed.

Keywords: Spinel, Refractories, Steel ladle, Slag corrosion, Thermomechanical properties

SUROWCE SPINELU MAGNEZOWO-GLINOWEGO NA WYSOKIEJ JAKOŚCI MATERIAŁY OGNIOTRWAŁE STOSOWANE W KADZIACH STALOWNICZYCH

Produkcja stali o wysokiej jakości wymaga długotrwałej obróbki stali w kadzi stalowniczej. Ma to niezwykle wpływ na materiały ogniotrwałe kadzi stalowniczej, np. na potrzebę wysokiej jakości funkcjonalnych materiałów ogniotrwałych jak w przypadku korków spustowych. Zmiany eksploatacyjne, takie jak zwiększone temperatury spustu, dłuższe czasy przetrzymywania i bardziej agresywna rafinacja pozapiecowa, przekładają się na zapotrzebowanie na bardziej cienkie wyłożenia ogniotrwałe i dłuższe czasy użytkowania materiałów ogniotrwałych. Te połączone czynniki prowadzą do pojawienia się na nowo zainteresowania surowcami spinelu magnezowo-glinowego.

Spinele magnezowo-glinowe wykorzystywane są od wielu lat jak materiał ogniotrwały przy produkcji stali, w wielu różnych postaciach. Artykuł ten stanowi przegląd sposobów wytwarzania, właściwości i jakości spineli. Przedyskutowano również aktualny postęp w wykorzystaniu spineli.

Słowa kluczowe: spinel, materiały ogniotrwałe, kadź stalownicza, korozja żużlowa, właściwości termo-mechaniczne

Introduction

This paper discusses the structure, properties and applications of magnesium aluminate spinels, with particular reference to their advantages in formulating refractories for clean-steel.

Magnesium aluminate spinels are increasingly being used in refractories for steel-making due to their particular combination of resistance to steel-making slag corrosion, thermal shock resistance and excellent hot strength. Spinel refractories were initially (mid-1960's) produced by the *in situ* reaction of alumina with periclase in magnesia bricks for linings of cement kilns. The availability of high-quality pre-reacted spinels has opened the possibilities of developing high purity refractories in both monolith and brick form.

Properties: Structure

Magnesium aluminate spinel is a member of a group of oxides that have the same crystal structure, which is named the spinel structure. The spinel group contains over twenty members, but only a few are considered common.

The general formula of the spinel group is AB_2O_4 , where A represents a divalent metal ion such as magnesium, iron, nickel, manganese and/or zinc, and B represents trivalent metal ions such as aluminium, iron, chromium or manganese. Unless otherwise described, the term "spinel" in this paper will refer to $MgAl_2O_4$, the mineral spinel, which is the only compound in the binary system $MgO - Al_2O_3$.

A strong feature of this group of minerals is the tendency for substitutional solid-solutioning, where large percentages of one or both of the spinel components may be substituted by others of the group without modification of the crystal structure, or indeed any significant strain on the crystal lattice. Both magnesium and aluminium cations can be replaced by others with similar size, keeping the electrochemical balance. Thereby a wide range of solid solutions results for the spinel group members. Additionally, the $MgAl_2O_4$ structure shows an increasing phase region with increasing temperature, especially towards higher alumina contents. Electrochemical balance is achieved by vacancies at metal-cation and oxygen-anion sites in the structure. This feature will be discussed later as playing a major factor in the advantage of spinel for resistance to steel-making slags.

Physical Properties

Magnesium aluminate spinel is a highly refractory material, with a melting point of 2135°C. Table 1 shows a comparison of the density, thermal expansion coefficient and thermal conductivity of the end-members (MgO , Al_2O_3) compared to the spinel phase. The differences between these phases in thermal expansion are responsible, in part, for the superior thermal shock resistance of spinel. The decrease in density or the increase in specific volume as spinel forms from the end-members needs to be considered for technical applications, e.g. in castables, where spinel is formed *in situ* from MgO and Al_2O_3 components. These effects and their influence on performance will be discussed in more detail in a later section.


Table 1. Physical properties of spinel, MgO and Al_2O_3 [1].
Tabela 1. Właściwości fizyczne spinelu, MgO i Al_2O_3 [1].

		Spinel MgAl_2O_4	Periclase MgO	Corundum Al_2O_3
Density	g/cm^3	3.58	3.58	3.99
Thermal conductivity	$\text{W/m}\cdot\text{K}$	5.9	7.1	6.3
Thermal Expansion Coefficient	$\text{dL/L}\cdot\text{K}\cdot 10^6$	7.6	13.5	8.8

Manufacturing

Natural sources for spinel as refractory raw material are not known therefore spinels must be produced synthetically. The two main routes for spinel production are sintering and fusion. Most refractory grade spinels are made from a combination of high-purity synthetic aluminium oxide and chemical-grade magnesium oxide. Synthesis takes place either in a shaft kiln for sintered spinel, or an electric arc furnace for fusion. Very fine and reactive raw materials are required, as the formation of spinel in the solid state is kinetically difficult. The advantage of sintered spinel is that this is a continuous ceramic process, with controlled feed-rate and uniform temperature distribution in the kiln, leading to a very homogeneous product with crystal sizes of 30–80 μm and low porosity (<3%). On the other hand, production of spinel by fusion is typically a batch process. The large ingots require extended cooling time, which leads to inhomogeneities in the microstructure as the poured ingot cools. At the outside, spinel crystals are smaller due to the faster cooling than towards the inside. In the centre, the impurities are concentrated due to the lowest melting point. Therefore, homogeneous fused spinel materials can only be achieved by careful selection of processed material.

The use of high-purity raw materials leads to another advantage of spinel – typically, these aggregates are low in impurities ($\text{MgO} + \text{Al}_2\text{O}_3 > 99\%$), particularly silica content, which contributes to the excellent high-temperature properties. Bauxite-based spinels have been evaluated by several sources. Moore *et al.* [2] determined that experimental spinels based on bauxite and diasporite exhibited high-steady-state creep rates when compared to the synthetic alumina based spinel. The creep rate is attributed to the high level of glass formed in the aggregate by the impurities in the bauxite

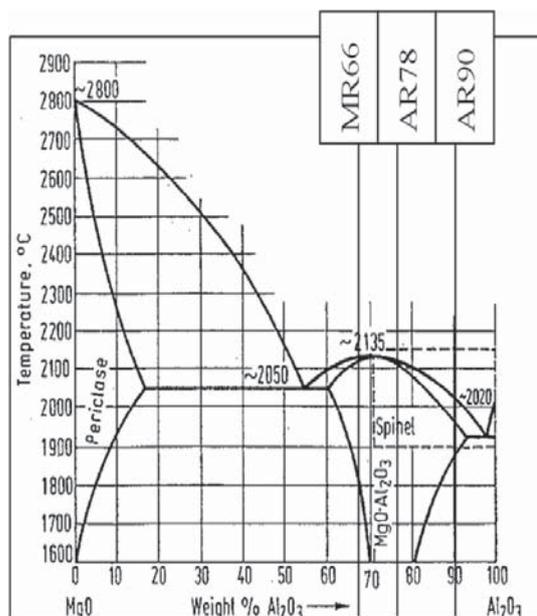

		MR 66	AR 78	AR 90
MgO content (typical values)	%	32.0 - 33.5	22.0 - 23.0	9.0 - 10.0
Bulk Specific Gravity (typical)	g/cm^3	3.26 - 3.29	3.25 - 3.29	3.38 - 3.42
Apparent Porosity (typical)	%	1.2 - 2.0	1.5 - 2.0	1.5 - 2.5

Fig. 1. Alumina-magnesia phase diagram [3] and typical spinel properties (Almatis).

Rys. 1. Diagram fazowy Al_2O_3 - MgO [3] i typowe właściwości spinelu (Almatis).

(SiO_2 , TiO_2 , Fe_2O_3 , alkalis). Bauxite spinels do not provide the performance of synthetic alumina based spinels and can be used only in areas where low resistance to erosion or low hot strength is not a concern.

Product types

Commercial spinel products are split into two groups either side of the stoichiometric ratio of 71.8% Al_2O_3 /28.2% MgO (Fig. 1). Magnesia rich MR 66 contains excess MgO , whereas alumina rich AR 78 and AR 90 contain excess alumina. Due to the spinel phase region, at high temperatures up to 1900°C a spinel phase containing 90% Al_2O_3 can be produced and maintained by rapid cooling. At lower temperatures, e.g. 1600°C during steel production, this high alumina content in AR 90 becomes unstable and a mixture of spinel and free corundum (Al_2O_3) is formed. The AR 78 spinel phase remains stable at temperatures around 1600°C. Towards MgO , the solid solutioning of the spinel phase is much less, so that MR 66 by purpose contains traces of periclase (MgO).

Magnesia-rich (MR) spinels

The properties and applications of magnesia-rich spinels are controlled by the presence of traces of periclase. As MR 66 does not contain free alumina, no further spinel formation and undesired volume expansion can occur when added to magnesia bricks. MR 66 additions to magnesia bricks, e.g. for cement rotary kilns, remarkably improve the thermal shock resistance (TSR) and can replace chrome ore additions to

overcome health concerns against chromium containing refractories in various regions worldwide. The mechanism to improve the TSR is the lower thermal expansion of spinel vs. periclase, which leads to the formation of microcracks, acting as crack arrestors.

The MgO traces in MR 66 preclude the option of using magnesia-rich spinel as a component of aqueous systems such as castables, as hydration of the periclase may lead to brucite ($\text{Mg}(\text{OH})_2$), and the consequent volume change leads to cracking in cast pieces. Magnesia-rich spinel is used in cement kiln applications, particularly in nose-rings and hot-zones.

Alumina-rich spinels

Alumina-rich spinels are the largest volume of the refractory spinels, as they are used as components of refractories for steel production. Their use is driven by two main sets of properties; thermal characteristics, such as improvements to hot strength and to thermal shock resistance; and resistance to corrosion by steel-making slag. Additions of high purity alumina rich spinels to alumina castables remarkably improve the hot strength as shown in Fig. 2.

Spinel content of 15-30 mass %, which corresponds to MgO content of 4-10 mass %, is commonly used. Recent developments as reported by Franken *et al.* [4] in the use of fired spinel refractories, e.g. in steel ladles, have indicated up to a 60% reduction in lifetime when comparing low-silica (<0.1% SiO_2) to high silica (1.0% SiO_2) spinel brick. This demonstrated that optimal performance can only be expected from high purity synthetic materials.

The slag resistance of alumina-rich spinels is one of the most important properties, and the primary reason for the use of spinel in steel-making refractories. Alumina rich spinels, e.g. AR 78 and AR 90 with alumina contents of 78 and 90 mass %, respectively, incorporate into the spinel crystal structure (either at vacant lattice sites or in substitution for MgO) low-melting, low-viscosity components like MnO and FeO in the infiltrated slag (Fig. 3). As the slag composition becomes deficient in FeO and MnO the slag viscosity increases, and has a much lower tendency for penetration and erosion.

For a spinel that is more alumina-rich, such as AR 90, the Al_2O_3 rich spinel solid solution becomes thermodynamically unstable at the steel making temperatures and alumina is released from the spinel (Fig. 4). The alumina reacts with CaO from the slag to form an inter-granular phase, calcium hexaluminate (CA_6). CA_6 is a very refractory phase (onset of melting at 1875°C), and in addition the reaction exhibits a volume expansion, causing a reduction in refractory surface porosity and reducing the tendency for slag penetration.

Experimental tests of slag resistance were carried out using basic ($C/S = 2.3$) and acid ($C/S = 0.3$) slags in an induction furnace at 1600°C. Refractory formulations with and without spinel additions were developed, cast and placed as the lining of induction furnace. Upon completion of the test the experimental bars were sectioned for evaluation of slag penetration and slag erosion. Results are shown in Fig. 5. These demonstrate the superior performance of spinel-containing refractories under conditions of severe slag attack. With spinel addition, slag infiltration as well as corrosion at the metal/slag interface can be remarkably reduced.

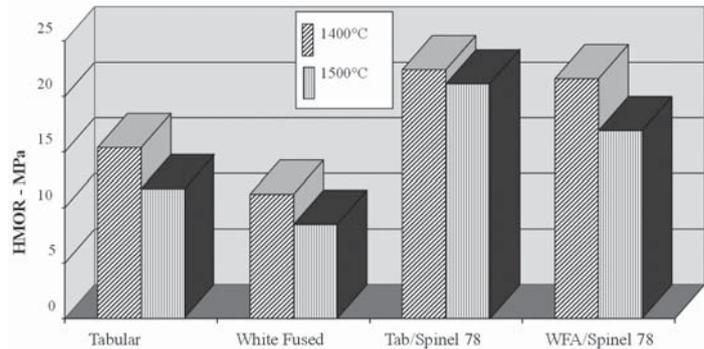


Fig. 2. Hot modulus of rupture values for high alumina castables with spinel additives.

Rys. 2. Wartości umownej wytrzymałości na gorąco w przypadku wysokoglinowych betonów ogniotrwiałych z dodatkami spinelu.

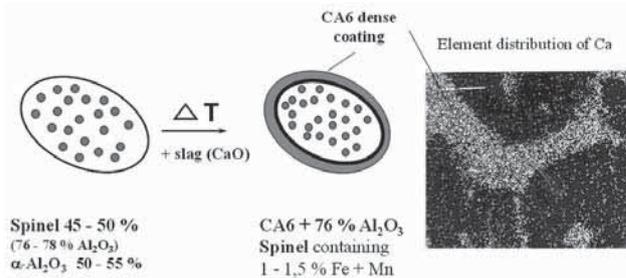


Fig. 3. AR 78 grain composition and slag reaction.

Rys. 3. Skład ziarnowy AR 78 i reakcja z żużlem.

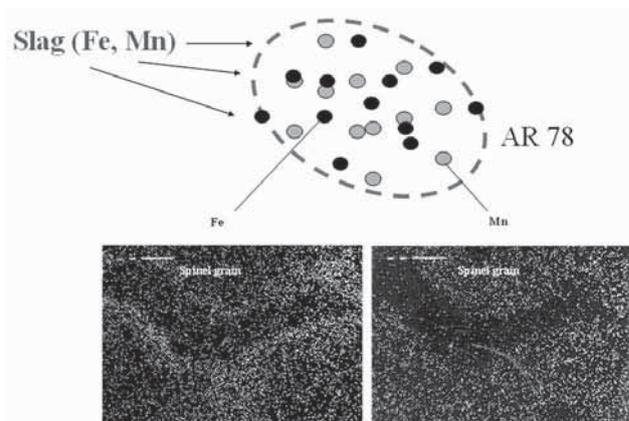


Fig. 4. AR 90 grain composition and slag reaction.

Rys. 4. Skład ziarnowy AR 90 i reakcja z żużlem.

Of particular relevance is the placement and type of spinel addition to refractories for optimization of slag resistance. The presence of AR 78 spinel in the fines promotes the resistance to slag corrosion most effectively and as well improves the thermal properties such as hot strength. It is informative to note that a similar weight percentage of spinel in the coarser fractions does not impart the same level of property enhancement. Therefore, AR 78 products with 45 and 20 μm fineness are of special interest. AR 90 spinel does provide a further performance enhancement, if it replaces e.g. tabular alumina in the coarse sizes of the formulation. Extended market experience has confirmed the benefits of AR 78 in the fines and AR 90 in the coarse fractions of alumina castables.

Itose *et al.* [5] reported similar improvement in corrosion and penetration resistance by adding fine spinel powder to alumina-spinel castables. They compared spinel castables

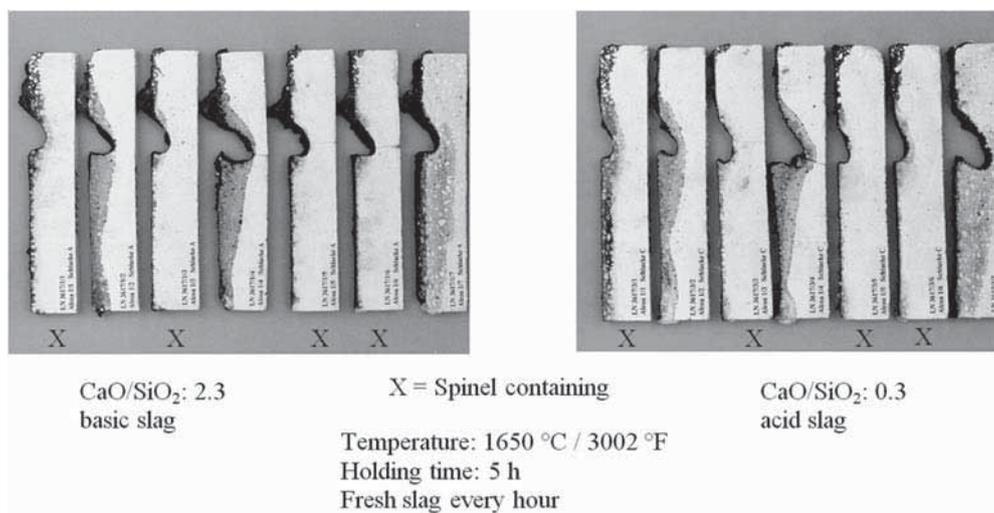


Fig. 5. Slag corrosion tests – induction furnace.
Rys. 5. Badania korozji żuźlowej – piec indukcyjny.

Table 2. Effect of pre-reacted spinel vs *in situ* spinel on thermomechanical properties (RuL = refractoriness under load (0.2 MPa)).
Tabela 2. Wpływ spinelu przereagowanego wcześniej w zestawieniu ze spinelem *in situ* na właściwości termomechaniczne (RuL = ogniotrwałość pod obciążeniem (0,2 MPa)).

			Self flow LCC	Self flow LCC	Self flow LCC
			Tabular alumina	Alumina-spinel	Spinel forming
Chemistry	Al ₂ O ₃	wt%	98	93	92
	MgO	wt%		5	6.4
	SiO ₂	wt%	<0.05	<0.05	0.5
	CaO	wt%	1.5	1.5	0.7
Mixing water		%	5.0	5.3	5.0
HMoR @ 1500°C		MPa	17	23	2
RuL	Max Def (Dmax)	%	1.02	1.10	1.24
	T @ Dmax	°C	1540	1700	1250
	T 0.5%	°C	1690	>1700	1360
	T 2%	°C	>1700	>1700	1655

with up to 20% addition of fine spinel and observed a decrease in the corrosion and penetration indices of approximately 40-50%.

Advantages of pre-reacted spinel vs *in situ* spinel forming

There are several examples where *in situ* spinel formation is formulated as part of the castable, possibly to reduce cost. However, there are significant disadvantages to this approach. The formation of spinel from alumina and magnesia leads to a remarkable volume expansion. Theoretically, this volume expansion will be 13%, based on a relative density calculation. In practice, however, this expansion is around 5%, still excessive for the microstructure to accommodate without cracking. Addition of fine silica, such as microsilica, is often utilized to promote liquid-phase sintering, and to allow some local deformation to overcome the volume expansion. However, the residual glassy phase will have a significant effect on the hot strength, as seen in Table 2.

The effect of spinel addition and the use of microsilica on the thermomechanical properties

can be more dramatically seen graphically, as shown in Fig. 6.

In a ladle sidewall, spinel-forming castables show benefits. The volume expansion due to *in situ* spinel formation is said to contribute to a densification of the surface layer. Also the liquid phase formation due to the silica additions increases the mechanical flexibility of the castable, which can be beneficial to avoid cracking of the lining during pick-up and set-down of the hot ladle. In general, because ladle

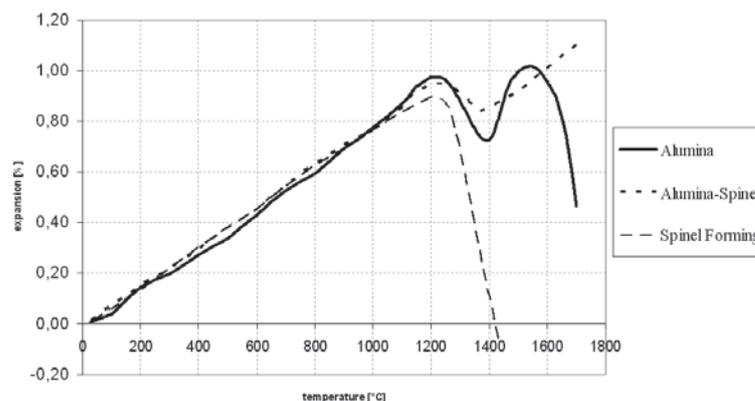


Fig. 6. Refractoriness under load 0.2 MPa, pre-fired at 1000°C.
Rys. 6. Ogniotrwałość pod obciążeniem 0,2 MPa, próbki wstępnie ogrzano w 1000°C.

Table 3. Model cost calculation for a monolithic 200 t steel ladle bottom using 5 t high alumina castable.

Tabela 3. Modelowa kalkulacja kosztu w przypadku 200 t monolitycznej kadzi przy najniższym zużyciu wysokoglinowego betonu wynoszącym 5 t.

Castable material		Bauxite	Brown Fused Alumina	Tabular Alumina	Tabular Alumina + Spinel
Castable price	%	100	120	155	165
Lining life	heats	45	65	90	120
Steel produced	t	9,000	13,000	18,000	24,000
Specific refractory costs per t steel	%	100	85	77	62

sidewalls are less subjected to erosion than a ladle bottom, the lower hot strength of the *in situ* castable is less of a factor. However, poor tapping practices and/or extensive stirring can cause significant higher sidewall erosion, and spinel-forming refractories with high silica contents will then exhibit higher erosion rates.

For pre-cast shapes, spinel-forming formulations are not preferred, due to hydration of the magnesia additive. Also, many pre-cast shapes are used in areas of high erosion, such as impact areas, purging plugs and well blocks. The reduced erosion resistance of *in situ* spinel formulations would reduce the life and increase operating cost.

Applications

Spinel additions remarkably increase the performance of alumina refractories and contribute to more cost effective lining concepts. Typical spinel applications are steel ladle linings, impact pads, purging cones and well blocks, nozzles, wears and dams, lances, and slide gates. Other spinel applications to be mentioned are glass refractories. However, here stoichiometric spinel compositions are preferred.

To illustrate the cost/benefit considerations of high purity synthetic raw materials and spinel refractories, the following model cost calculation of a monolithic steel ladle bottom has been set up as an example, which does not refer to a specific steel plant. The figures are based on an estimation of typical market prices of castables including the lining procedure services. The lining life of the different concepts is estimated based on performance experiences with such types of refractories [6]. Although the price level of high purity, synthetic raw material based refractories is higher when compared to natural raw materials, their superior performance provides much higher lining life and reduces the specific costs of the refractory per ton of steel as shown in Table 3. A reduced maintenance effort due to higher lining life has not been included in this model calculation. Although the price of spinel refractories is higher, the performance increase clearly overcomes that and even more favourable specific costs can be achieved.

New Materials

Since the mid-1990's, there has been extensive work on the placement of refractory castables by pumping and/or shotcreting. Both of these techniques rely on the ability of the refractories manufacturer to formulate a mix that can resist the high shear rate of a piston-type pump through a narrow (75-100 mm) diameter hose. The vast majority of such mixes utilizes the particular benefits of microsilica to reduce the shear stress and allow the castables to be pumped without exhibiting the dilatant behaviour that can cause the material in the hose to

become a solid mass. As the presence of silica, together with other components of the pumpable castables, can significantly reduce the hot-strength of such products, there have been many attempts to develop castables based on high-purity systems that do not exhibit this dilatancy. Experiments on fine high-purity matrix materials have led to the development of the new reactive alumina-spinel product E-SY 2000. This new product can be used to replace the fine components of high-purity alumina-spinel refractories and allow them to be pumped with low resistance to shear stresses.

Conclusions

High quality pre-reacted magnesium aluminate spinels improve the performance of refractories in various applications. Magnesia rich spinels are primarily used for magnesia based refractories and used extensively in cement kilns. Since high purity alumina rich sintered spinels became available in the 1990's, spinel additions to alumina refractories, especially in monolithic refractories, are of increasing importance. Both the slag resistance in steel applications and the thermomechanical properties are remarkably improved, which contributes to more cost effective refractory solutions. Spinel additions in the fine fraction of the formulation show the highest benefit. Most recent developments are aimed at developing low dilatancy, pumpable alumina-spinel castables, which do not require any fumed silica additions and provide all advantages of high purity spinel refractories.

New application techniques, such as pumping and shotcreting, can be developed with high-purity alumina materials using newly developed reactive alumina-spinel products designed to reduce the tendency for dilatancy.

References

- [1] Bartha P.: "Spinell und spinellhaltige feuerfeste Werkstoffe" in Berichtsband Feuerfesttechnik – Werkstoffe, Rohstoffe, Neue Entwicklungen, Verlag Stahleisen mbH, Düsseldorf, 1984, 113-133.
- [2] Moore R.E., Monton B.S., Caballero A.: "Creep Behavior of Synthetic Spinels Based on Raw Diaspore and Bauxite", 29th Annual Meeting of St. Louis Section, American Ceramic Society, 1993.
- [3] Muan A., Osborn E.F.: "Phase Equilibria Among Oxides in Steel-making", Addison-Wesley Publishing Company, Inc., 1965.
- [4] Franken M.C., Siebring R., de Wit T.W.M.: "New refractory Lining for Steel Ladle BOS no. 2 Corus IJmuiden", Unitec 2001.
- [5] Itose S., Nakashima M., Isobe T., Shimizu I.: "Improvement in the Durability of Alumina-Spinel Steel Ladle Castable Containing Spinel Fine Powder," Journal of the Technical Association of Refractories, Japan, 22, [1], (2002), 26-30.
- [6] Buhr A.: "Refractories for Steel Secondary Metallurgy", CN-Refractories, 6, [3], (1999), 19-30.

